

Selvol™ 425 Polyvinyl Alcohol for Improved Oil Resistance and Ink Holdout

Polyvinyl Alcohol Technical Bulletin



Polyvinyl alcohol (PVOH) is an extremely hydrophilic polymer, and as a continuous film, exhibits total barrier properties to oils, greases and most organic solvents.

On paper and paperboard substrates, however, the add-on level of PVOH is limited by its viscosity to very low percentages based on dry fiber weight. Thus, true barrier properties are never achieved. But, even at low add-on levels, PVOH finds use in meeting papermaker's oil resistance needs, usually to a defined specification standard.

Selvol PVOH is used on a variety of paper and paperboard grades for the purpose of controlling oil penetration, as in food grade

applications, or to control ink penetration and feathering on uncoated printing and writing grades. Following are two commercial examples:

- 1) A recycled paperboard mill achieved a 20-unit Vanceometer improvement by switching to a 70/30 starch/PVOH formulation from a straight starch system.
- 2) A solid, bleached paperboard mill achieved an 80 Vanceometer specification, unobtainable with starch alone, by switching to a 60/40 starch/PVOH formulation.

Laboratory Studies

These experiences typify the superiority of PVOH over starch. Laboratory studies have demonstrated that this superiority is due to the ability of PVOH to more effectively reduce the porosity of the sheet. Figure 1, for example, compares Selvol 425, Selvol 325 and a hydroxyethylated starch as surface sizes on a 73-pound remailer grade of paper. Starch was applied at solids levels of up to 14% in 2% increments, and the two PVOH grades, differing only in degree of hydrolysis, were applied at up to 8% solids in 1% increments. When compared at any equal solids level, both PVOH grades demonstrated dramatically less porosity than the starch treatment. Note also that, of the two PVOH

Selvol™ 425 Polyvinyl Alcohol for Improved Oil Resistance and Ink Holdout

grades, the lower percent hydrolysis grade, Selvol 425, demonstrated significantly less porosity.



Figure 2 shows that this air porosity reduction improvement correlates directly to improved oil resistance. Selvol 425, 325 and 125 (see table) were applied to four different substrates at 5% solids by means of a laboratory Keegan size press, and the treated sheets were then tested for Mazola oil drop holdout. Note that on all four substrates, Selvol 425 exhibited much better oil holdout.

These results have been confirmed in many other evaluations, including K&N ink holdout, Magic Marker pen holdout, ink feathering control,

chocolate resistance, Vanceometer oil holdout, the 3M Kit test and the TAPPI Turpentine Test T 454-OM-84.

Selvol PVOH Typical Properties		
	% Hydrolysis	Viscosity, cps*
Selvol 425	95.5-96.5 (intermediate)	27-31
Selvol 325	98.0-98.8 (fully)	28-32
Selvol 125	99.3+ (super)	28-32

*4% Aqueous solution, 20 °C

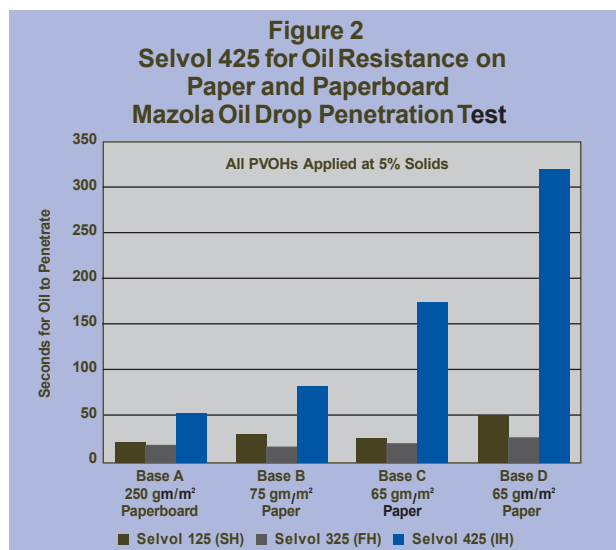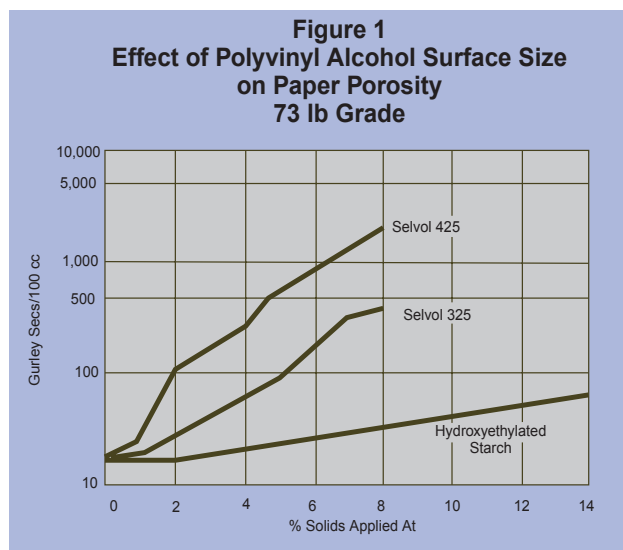

International Offices

North America:

Sekisui Specialty Chemicals America
1603 West LBJ Freeway
Dallas, TX 75234-6034
Tel +1-972-277-2901
Fax +1-972-277-2907
www.sekisui-sc.com

Europe:

Sekisui Specialty Chemicals Europe S.L.
Ctra. N-340 Km. 1157 Apdo. 1388
43080 Tarragona
Spain
Tel +34 977549899
Fax +34 977544982

Visit www.selvol.com for more information about our products.

To the best of our knowledge, the information contained herein is accurate. However, neither Sekisui nor any of its affiliates assumes any liability whatsoever for the accuracy or completeness of the information contained herein. Final determination of suitability of any material and whether there is any infringement of patents is the sole responsibility of the user. All chemicals may present unknown health hazards and should be used with caution. Although certain hazards may be described in this in this publication, we cannot guarantee that these are the only hazards that exist. Users of any chemical should satisfy themselves by independent investigation of current scientific and medical knowledge that the material can be used safely. In addition, no certification or claim is made as to the status, under any law or regulation, including but not limited to the toxic Substances Control Act, of either the chemicals discussed above or any subsequent polymerization or reaction products that result from a formulation containing them.